arXiv:cond-mat/0407026v1 [cond-mat.str-el] 1 Jul 2004

Orbital Glass in $FeCr_2S_4$

V. Tsurkan[a,b], V. Fritsch[a], J. Hemberger[a], A. Krimmel[a], M. Mücksch[a], N. Büttgen[a], H.-A. Krug von Nidda[a], D. Samusi[b], S. Körner[a], E.-W. Scheidt[a], M. Honal[a], S. Horn[a], R. Tidecks[a], and A. Loidl[a]
[a] *Institut für Physik, Universität Augsburg, D- 86159 Augsburg, Germany and*
[b] *Institute of Applied Physics, Academy of Sciences of Moldova, MD-2028, Chisinau, R. Moldova*[*]

(Dated: February 2, 2008)

Low-temperature heat-capacity investigations on the spinel $FeCr_2S_4$ with ferrimagnetic spin order and orbitally degenerated Jahn-Teller active Fe^{2+} ions in a tetrahedral crystal field, provide experimental evidence of an orbital liquid state above 10 K. We demonstrate that the low-temperature transition at 10 K arises from orbital order and is very sensitive to fine tuning of the stoichiometry in polycrystals. In single crystals the orbital order is fully suppressed resulting in an orbital glass state with the heat capacity following a strict T^2 dependence as temperature approaches zero.

PACS numbers: 75.50.Pp, 75.50.Gg, 75.40.-s, 71.70.Ej

Orbital physics has become a fascinating topic in modern solid-state physics. The spatial orientation of orbitals governs the magnetic exchange and thus the long-range order of the spin degrees of freedom. If the orientational order of the orbitals can be changed by an external field (strain field or electric field), the magnetic order will be changed concomitantly. Such a tuning of electronic orbitals will be an important ingredient of a future correlated-electron technology [1].

Strong coupling of spin and orbital degrees of freedom yields complex ground states. Usually electron-phonon coupling lifts the orbital degeneracy and results in a long-range orbital order (OO) and in a change of the crystal symmetry via the Jahn-Teller (JT) effect [2]. In Mott-Hubbard (MH) insulators the OO may be also established by the Kugel-Khomskii mechanism [3], where the orbital degeneracy is removed via a purely electronic interaction. However, recently it has been suggested that the exchange in orbitally degenerate systems is strongly frustrated and in cubic lattices the orbitals may remain disordered down to zero temperature, forming an orbital liquid (OL) [4, 5]. Indeed, an OL state has been proposed for $LaTiO_3$ [6, 7], but has been questioned recently [8, 9]. To find new OL's, it seems promising to search for systems with strong correlation effects and weak JT coupling. The appropriate candidates are MH insulators with electrons with threefold degeneracy in octahedral or twofold degeneracy in tetrahedral crystal fields [10], and where in addition the orbitals are coupled via strongly frustrated exchange interactions induced by disorder or geometric frustration. Frustration results in a dynamic liquid ground state or in a glassy freezing of the internal degrees of freedom at low temperatures. As well established by numerous studies, frustration yields a spin-glass state for structurally disordered spin systems [11], while in geometrically spin-frustrated [12] compounds it results in a low-temperature spin-liquid [13] or spin-ice [14, 15] state. In contrast, reports on OL or JT-glasses, i.e. orbital glasses (OG), are rare [16, 17, 18], although OO has been observed in a variety of *d*-electron systems.

Here we provide experimental evidence for an orbital liquid and an orbital glass state in a ferrimagnet with perfect spin order. We focus on the orbital degrees of freedom of the magnetic semiconductor $FeCr_2S_4$ which recently attracted considerable attention due to its colossal magnetoresistance effect [19]. It crystallizes in a normal spinel structure AB_2S_4 (space group $Fd\bar{3}m$) in which S^{2-}-anions build a cubic close-packed *fcc* lattice, Fe^{2+}-cations occupy 1/8 of the tetrahedrally coordinated A-sites, and Cr^{3+}-cations occupy 1/2 of the octahedrally coordinated B-sites. The Cr^{3+} sublattice (electronic configuration $3d^3$, spin $S = 3/2$), is dominated by ferromagnetic exchange of the 90° Cr-S-Cr bond angle. The Fe^{2+} ions ($3d^6$, $S = 2$) are only weakly coupled within the sublattice, but much stronger to the Cr ions [20]. Below the Curie temperature, $FeCr_2S_4$ reveals a ferrimagnetic spin order with the Fe^{2+} and Cr^{3+} magnetic moments aligned antiparallel to each other [21]. Concerning the orbital degrees of freedom, the orbital moment of the Cr^{3+} ion is quenched. The lower orbitally degenerated e-doublet of Fe^{2+} is JT active allowing for a distortion of the ideal FeS_4 tetrahedron in order to lower the symmetry and, hence to lift the degeneracy [22]. Indeed, an abrupt change of the electric field gradient detected in Mössbauer experiments [23] on polycrystalline $FeCr_2S_4$ at 10 K was attributed to a transition from a dynamic into a static JT distortion below 10 K. Additionally, a λ-type anomaly of the specific heat C_p at 9.25 K [24] was registered on Fe-deficient samples. More detailed Mössbauer studies [25] have shown that the low-temperature anomaly cannot be explained in a single-ion picture alone but involves hybridization of the Fe^{2+} ground state with the nearest neighbour Cr^{2+} excited state. These results were interpreted in terms of a transition from orbital paramagnetism into orbital ferromagnetic order. Such an OO was also proposed based on band-structure calculations [26]. Recent ultrasonic experiments on $FeCr_2S_4$ single crystals revealed an elastic anomaly at 60 K, followed by a softening of the elastic moduli at lower temperature. Below 15 K an additional anomaly in the longitudinal modulus was observed [27]. These results also suggest a certain kind of OO.

The present paper focuses on the heat-capacity of $FeCr_2S_4$ single crystals and polycrystals with different stoichiometry tuned by heat treatments in vacuum and sulphur atmosphere. Polycrystals were prepared by solid-state reactions at 700°C from the high-purity elements. The as-grown polycrystals were obtained via repeated homogenisation sintering (4-5 times) followed by subsequent treatment in sulphur atmosphere (denoted as PC_{AG}). Some were annealed in vacuum at 700°C for two hours (PC_{VA}) and subsequently in sulphur atmosphere (PC_{SA}) at 700°C for 24 hours. Single crystals (SC) were grown by chemical-transport reaction at 820 - 850°C. Rietveld refinement of x-ray (CuK_α) powder-diffraction patterns confirmed the spinel structure and yielded a lattice constant $a_0 = 1.0005(1)$ nm and a sulphur fractional coordinate $x = 0.259(1)$ for the powdered single crystals. The respective values of $a_0 = 0.9997(1)$ nm for the polycrystals were found to coincide within the accuracy of the experiment. From a single-crystal x-ray diffraction analysis of 96 independent and altogether 2614 Bragg peaks, we determined the site occupancy of Fe:Cr = 1:1.99 and of Cr:S = 1:2.07, which reveals that the Fe:Cr ratio is almost ideal while Fe and Cr are slightly ($\sim 3\%$) under-stoichiometric when compared to the ideal sulphur network. An ICP (inductively coupled plasma) analysis of PC_{AG} yielded a nearly stoichiometric Fe:Cr:S ratio of 0.99:1.99:4.0. The magnetization was measured in a commercial SQUID magnetometer MPMS-7 (Quantum Design). The heat capacity was investigated in ^{4}He cryostats using adiabatic and relaxational techniques for $2 \leq T \leq 50$ K and in a $^3\mathrm{He}/^4\mathrm{He}$ dilution refrigerator using relaxational technique for $0.05 \leq T \leq 2.5$ K.

Figure 1 introduces the basic magnetic properties of $FeCr_2S_4$. It shows the temperature dependence of magnetization $M(T)$ for single (SC) and polycrystalline as-grown (PC_{AG}) samples at low fields. At the Curie temperature ($T_{\mathrm{C}} = 167$ K) the step-like anomaly in $M(T)$ reveals the onset of ferrimagnetic order. In the single crystal, a cusp at $T_m \approx 60$ K and a subsequent splitting of the field cooled (FC) and zero-field cooled (ZFC) magnetization indicate domain-reorientation processes [28]. While in the polycrystal the overall magnetization behavior is similar, distinct differences can be observed: here the ZFC and FC curves split already at T_{C} due to pinning of the magnetic domain walls by grain boundaries. The cusp-like anomaly is also present in the polycrystals, although shifted to higher T (≈ 75 K). Below this anomaly both the poly- and single crystals exhibit a pronounced downturn in the ZFC magnetization. However, only the polycrystal shows a clear step-like decrease (increase) in the ZFC (FC) magnetization at $T_{\mathrm{OO}} \approx 10$ K, which we ascribe to the OO transition. The accompanying magnetic anomaly at T_{OO} coincides with the low-temperature transition detected earlier by Mössbauer experiments in polycrystals [23, 25] associated with a JT-like transition resulting in long-range OO. The inset of Fig. 1 shows the field dependence of the magnetization $M(H)$ at $T = 4.2$ K for the $FeCr_2S_4$ single crystal. The saturation magnetization M_{s} of $1.88\mu_{\mathrm{B}}$ per formula unit (f.u.) is consistent with the ferrimagnetic order of Cr with $M_{\mathrm{s}}(2\mathrm{Cr}) = 6\mu_{\mathrm{B}}$/f.u. and Fe with $M_{\mathrm{s}}(\mathrm{Fe}) = 4.12\mu_{\mathrm{B}}$/f.u., taking into account the slightly enhanced g-value of Fe^{2+} ($g \approx 2.06$) due to spin-orbit coupling. Thus, a fully developed spin order below T_{C} is established, as was already shown by neutron-scattering studies [21]. Thus, the low-temperature anomalies are governed not by spin but by orbital degrees of freedom.

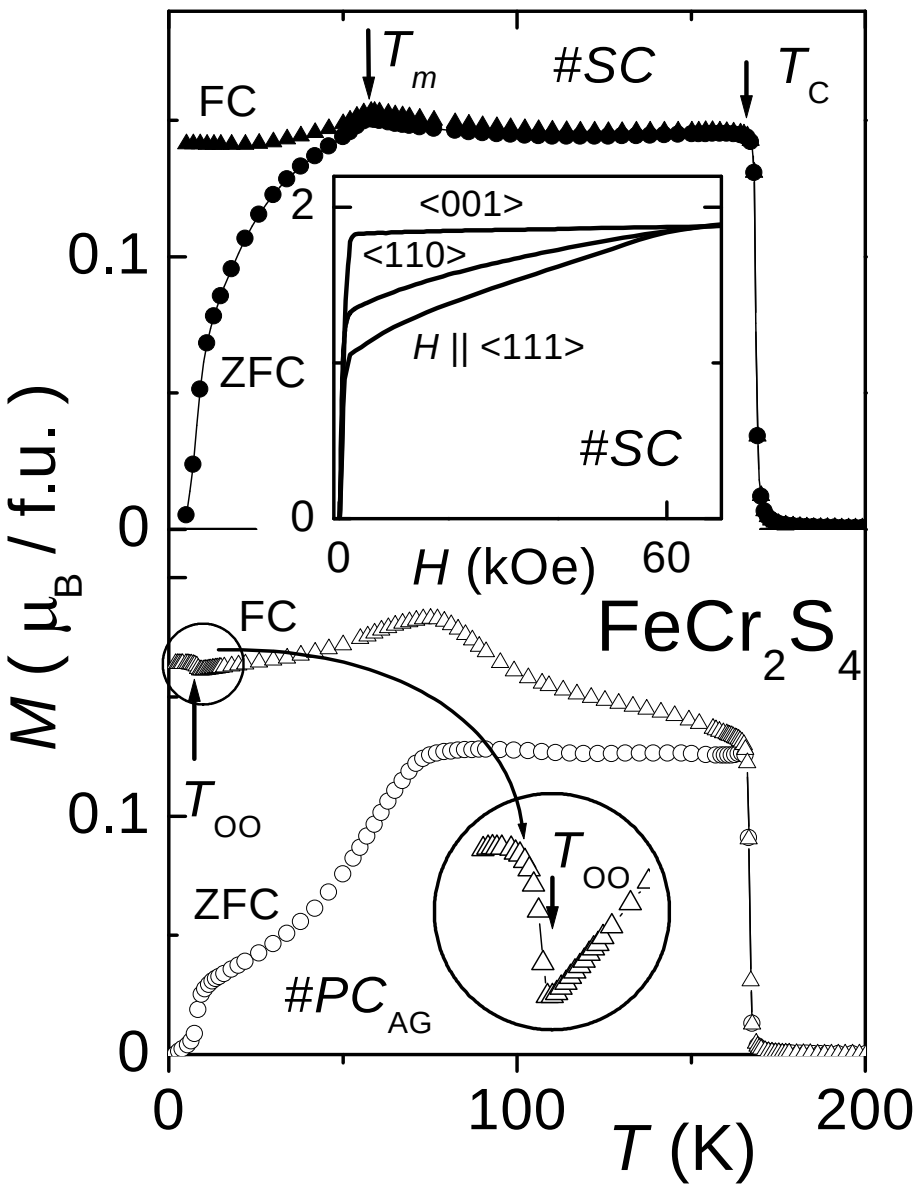

FIG. 1: Temperature dependence of the zero-field cooled (ZFC) and field cooled (FC) magnetization M in a field of $H = 100$ Oe for a $FeCr_2S_4$ single crystal (SC, upper frame) and in a field of 50 Oe for an as-grown polycrystal (PC_{AG}, lower frame). Inset: $M(H)$-dependence for H applied along easy $< 001 >$, intermediate $< 110 >$, and hard $< 111 >$ axes at 4.2 K for SC.

Figure 2 illustrates the principal results of the present investigation. The upper frame shows the specific heat at low T with axes C_p/T *vs.* T as measured in three polycrystalline samples after different heat treatment. The middle frame presents the specific heat of the single crystal. The vacuum annealed PC_{VA} and as-grown PC_{AG} polycrystals reveal well-defined OO transitions. In the sulphur-annealed PC_{SA} the phase-transition temperature is strongly reduced and the transition is smeared out. Moreover, the transition is completely suppressed in the single crystal. In the polycrystals the λ-type anomaly is followed by an exponential decrease of C_p with decreasing T, indicative of a gap opening in the orbital excitations. For the polycrystal PC_{VA} with the strongest C_p anomaly the data can be described within a BCS-like mean-field

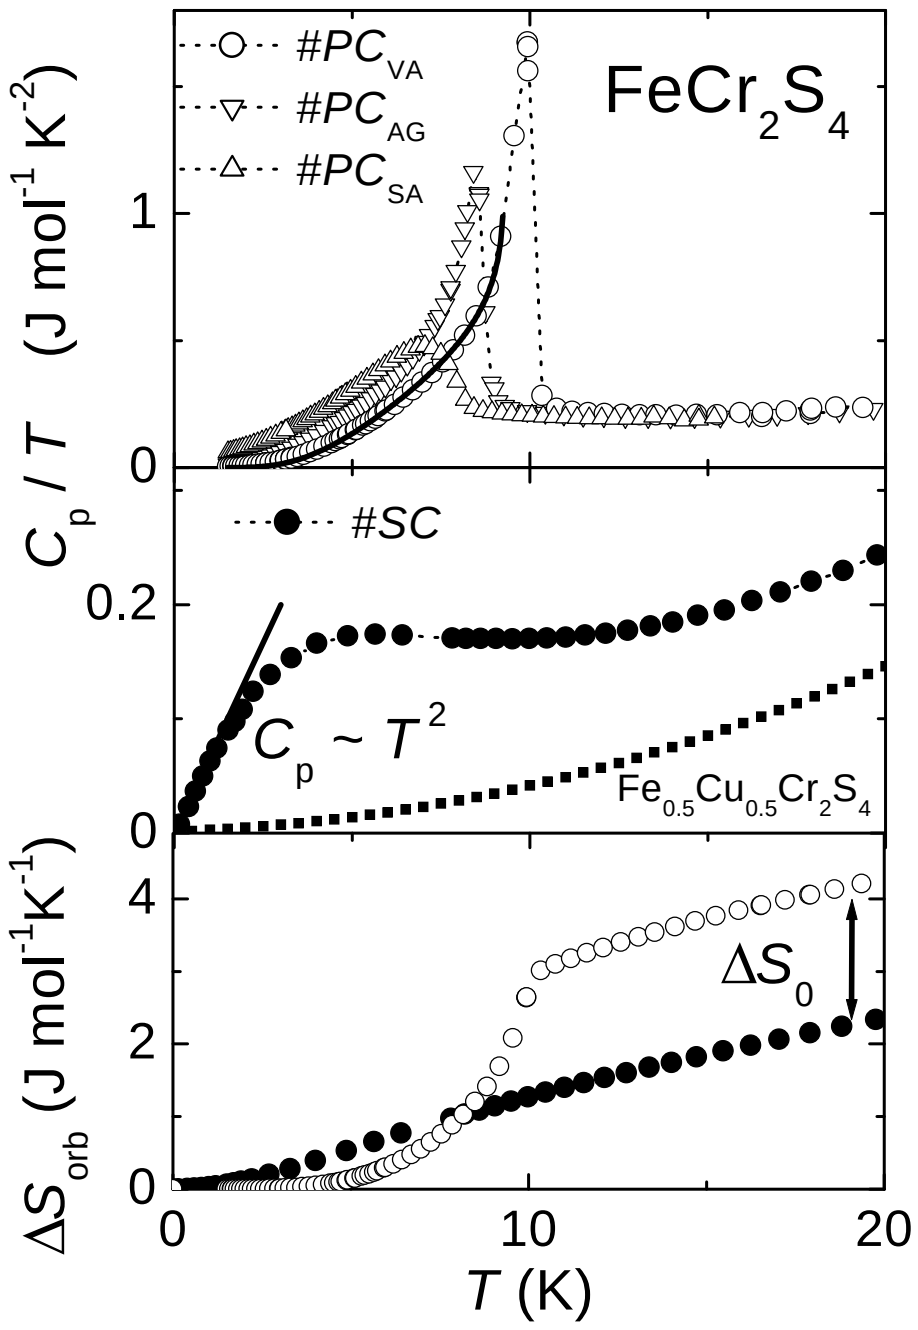

FIG. 2: Upper frame: T-dependence of C_p/T for polycrystals (open symbols) with different heat treatments: vacuum annealed ($PC_{\rm VA}$), as-grown ($PC_{\rm AG}$), and sulphur-annealed ($PC_{\rm SA}$). Solid line: mean-field fit with $T_{\rm OO} = 9.2$ K and $\Delta(T = 0)/k_{\rm B} = 11.4$ K. Middle frame: C_p/T of the single crystal (SC). Solid line indicates $C_p \propto T^2$ dependence. Solid squares: C_p/T of $\rm Fe_{0.5}Cu_{0.5}Cr_2S_4$. Lower frame: orbital entropy change $\Delta S_{\rm orb}(T)$ for the SC and the $PC_{\rm VA}$ calculated as described in the text.

approach using a T-dependent gap energy $\Delta(T)$ approximated by $\Delta(T) \approx 1.74\Delta_0(1 - T/T_{\rm OO})^{1/2}$. The best fit is obtained with the parameters $\Delta_0/k_{\rm B} = 11.4$ K and $T_{\rm OO} = 9.2$ K, yielding $2\Delta_0/k_{\rm B} \approx 2.5T_{\rm OO}$, which is reduced as compared to the BCS value, suggesting a weak coupling scenario.

On decreasing T, the specific heat in the single crystal passes through a cusp-shaped maximum and then approaches zero following a strict T^2-dependence. In canonical spin glasses a cusp-like maximum is also observed slightly above the freezing temperature, but a linear term evolves approaching $T = 0$ [11]. The T^2-dependence of the specific heat below the maximum is theoretically not expected for three-dimensional disordered spin-systems, but has also been observed in the geometrically frustrated spinel $\rm AlV_2O_4$ [29] as well as in geometrically frustrated two-dimensional spin glasses [30]. Ac-susceptibility measurements in $\rm FeCr_2S_4$ single crystals ruled out a spin-glass state [28]. Thus, the absence of the λ-type anomaly and the cusp-shaped maximum observed in $\rm FeCr_2S_4$ single crystals suggest a glassy-like state of the orbitals.

For $T > T_{\rm OO}$ all samples reveal a very similar specific heat with a highly enhanced linear term. This, however, cannot be explained by phonon or magnon contributions, which were estimated by measuring the specific heat of the related compound $\rm Fe_{0.5}Cu_{0.5}Cr_2S_4$, which has similar atomic mass and Debye temperature as $\rm FeCr_2S_4$. In this compound the Cu ions are monovalent and all Fe ions have a valence of 3+ ($3d^5$, $S = 5/2$) and hence are not JT active. It is a simple ferrimagnet whose specific heat can be well described by superposition of a T^3-law for phonons and a $T^{3/2}$-law for magnons. Comparison with $\rm Fe_{0.5}Cu_{0.5}Cr_2S_4$ thus reveals an additional linear contribution to the specific heat C_p of the order of $\Delta C_p/T \approx 100$ mJ/molK^2 in $\rm FeCr_2S_4$. It cannot be attributed to an enhanced Sommerfeld coefficient, because $\rm FeCr_2S_4$ is insulating at low T [19, 26]. Therefore, we ascribe it to strongly fluctuating orbitals. It is noteworthy that a linear term in the T-dependence of the heat capacity has been already predicted for the OL [31]. Furthermore, the existence of a dynamic JT effect had been originally deduced from Mössbauer experiments [23] and later was termed orbital paramagnetism regarding its cooperative properties involving the B-site Cr states [25]. The dynamic JT effect as well as orbital paramagnetism indicate orbital fluctuations and in their cooperative manner provide an OL state.

So far, we conclude that for $10\ {\rm K} < T < T_m$ in $\rm FeCr_2S_4$ an OL state is formed with fluctuating orbital arrangement, the average of which is probably detected as a softening of elastic constants below 60 K by ultrasound experiments [27]. The gap predicted for an OL in the orbital excitation spectrum [6] must be very small, as in the single crystal the linear term persists down to approximately 3 K and no exponential decay is observed at lower T. In polycrystals a transition occurs from the OL into the OO state at 10 K. In the single crystal the OO transition is suppressed and, taking into account the cusp-like maximum and decrease of the specific heat at lowest T, we suggest that the orbital degrees of freedom undergo a freezing transition into an OG state with randomly frozen-in orbital configurations.

The heat-capacity experiments in different external magnetic fields provide further support that the order-disorder transition in the polycrystal and the glassy freezing in the single crystal originate from the orbital degrees of freedom. Figure 3 illustrates the effect of an external magnetic field on the specific heat. The magnitude of the λ-anomaly in the polycrystal becomes slightly reduced, but without any noticeable shift in the ordering temperature. An increase of the specific heat becomes apparent just above $T_{\rm OO}$ only at 100 kOe. In the single crystal the specific heat is essentially field independent. If the λ-anomaly was related to a transition in the spin system, a much stronger influence of the magnetic field is expected, as e.g. observed in $\rm MnCr_2S_4$ [32]. Therefore, the λ-anomaly in the specific heat of $\rm FeCr_2S_4$ should be attributed to the onset of OO.

Now we turn to the evaluation of entropy for poly- and single crystals shown in the lowest frame of Fig-

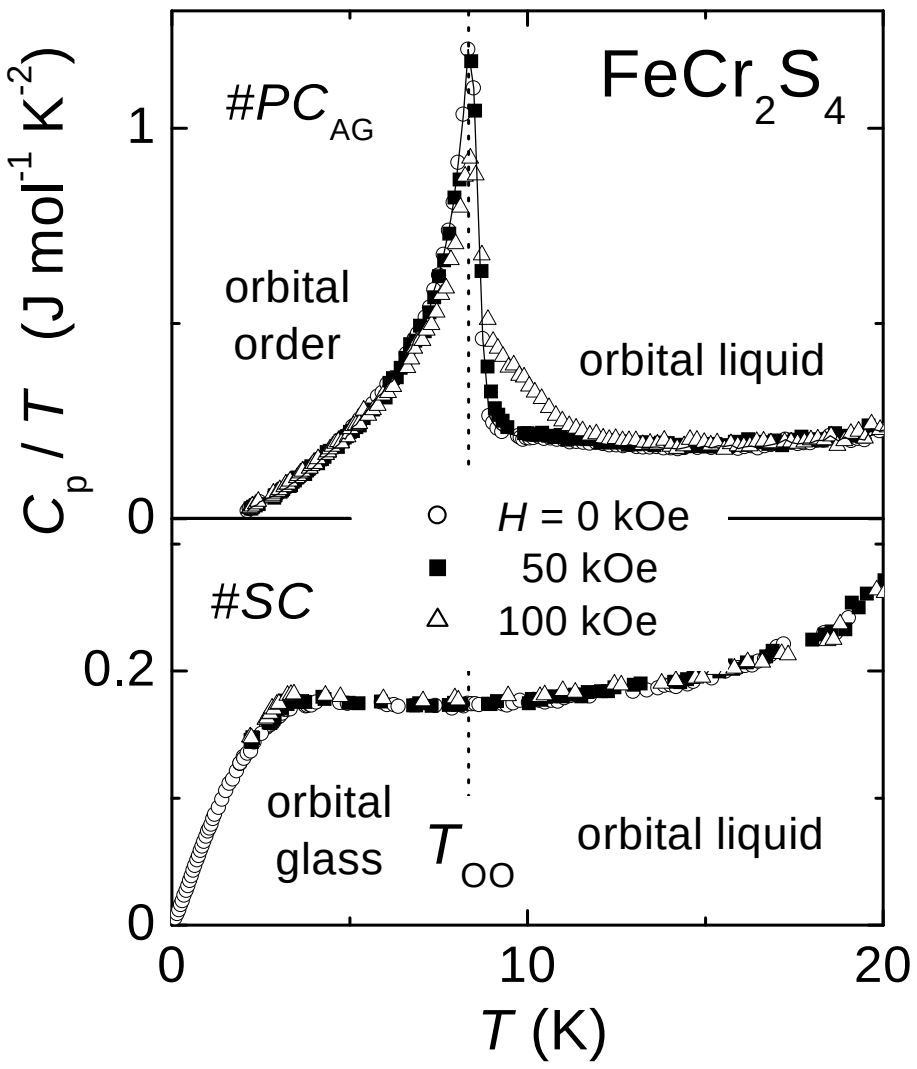

FIG. 3: T dependence of C_p/T for the as-grown polycrystal (PC_{AG}, upper frame) and single crystal (SC, lower frame) at different magnetic fields. Dash line: T_{OO} for PC_{AG}.

ure 2. The change of orbital entropy ΔS_{orb} has been obtained by integrating $\Delta C_p(T)/T$ for $0.1 \leq T \leq 20$ K. In the OO system (PC_{VA}), The orbital entropy S_{orb} should approach zero below the OO transition. Above T_{OO}, it is still increasing, indicating that the total value $R\ln 2 = 5.8$ J/molK assigned to the orbital doublet has not been fully recovered. It will be recovered at higher T due to increasing orbital fluctuations, as expected for an OL. For the single crystal the all-over change of orbital entropy below 10 K is about $\Delta S_0 = 2$ J/molK smaller than for the polycrystal. This difference of 1/3 of the total orbital entropy clearly demonstrates a macroscopic degeneracy of the ground state in the single crystal, which we interpret in terms of an orbital glass as T approaches zero.

This result surprisingly is quite similar to that observed in spin-ice systems [14]. Keeping in mind the observed T^2 dependence of the specific heat and the tetrahedral network of the Fe^{2+} ions, one may assume a certain role of geometrical frustration in the formation of the OG in the single crystal. To decide this definitely, a more precise knowledge of the orbital exchange is necessary and the connection between spin and orbital order needs further theoretical analysis.

In summary, our heat capacity study of $\mathrm{FeCr_2S_4}$ reveals a strong linear contribution $C_p \propto T$ in both poly- and single crystals suggesting an orbital liquid state. In polycrystals we observed a transition from this orbital liquid into an orbitally ordered state, which can be strongly shifted by fine tuning of the stoichiometry. In single crystals the orbital order is fully suppressed. We suggest that a transition from the orbital liquid into an orbital glass occurs, which is supported by the T^2-behavior of C_p on approaching $T = 0$. Thus, our results provide experimental evidence of such an orbital-liquid to orbital-glass transition in a $3d$-magnetic system.

This work was supported by the BMBF via VDI/EKM, FKZ 13N6917/18 and by DFG within SFB 484 (Augsburg).

---

[*] Electronic address: Vladimir.Tsurkan@physik.uni-augsburg.de
[1] Y. Tokura and N. Nagaosa, Science **228**, 462 (2000).
[2] H. A. Jahn and E. Teller, Proc. Roy. Soc. (London) A **161**, 220 (1937).
[3] K. I. Kugel and D. I. Khomskii, Sov. Phys. Usp. **25**, 231 (1982).
[4] S. Ishihara, M. Yamanaka, and N. Nagaosa, Phys. Rev. B **56**, 686 (1997).
[5] L. F. Feiner, A. M. Oles, and J. Zaanen, Phys. Rev. Lett. **78**, 2799 (1997).
[6] G. Khaliullin, Phys. Rev. B **64**, 212405 (2001).
[7] B. Keimer *et al.*, Phys. Rev. Lett. **85**, 3946 (2000).
[8] J. Hemberger *et al.*, Phys. Rev. Lett. **91**, 066403 (2003).
[9] M. Cwik *et al.*, Phys. Rev. B **68**, 060401 (2003).
[10] D. I. Khomskii and M. V. Mostovoy, J. Phys. A **36**, 9197 (2003).
[11] K. Binder and A. P. Young, Rev. Mod. Phys. **58**, 801 (1986).
[12] A. P. Ramirez, in *Handbook of Magnetic Materials*, edited by K. H. J. Buschow (Elsevier Science, Amsterdam, 2001), vol. 13, p. 423.
[13] B. Canals and C. Lacroix, Phys. Rev. Lett. **80**, 2933 (1998).
[14] A. P. Ramirez *et al.*, Nature **399**, 333 (1999).
[15] S. T. Bramwell and M. J. P. Gingras, Science **294**, 1495 (2001).
[16] M. A. Ivanov *et al.*, J. Magn. Magn. Mater. **36**, 26 (1983).
[17] F. Mehran and K. W. H. Stevens, Phys. Rev. B **27**, 2899 (1983).
[18] A. V. Babinskii *et al.*, JETP Lett. **57**, 299 (1993).
[19] A.P. Ramirez, R.J. Cava, and J. Krajewski, Nature **386**, 156 (1997).
[20] P. Gibart, J. L. Dormann, and Y. Pellerin, Phys. Stat. Sol. **36**, 187 (1969).
[21] G. Shirane and D. E. Cox, J. Appl. Phys. **35**, 954 (1964).
[22] L. F. Feiner, J. Phys. C: Solid State Phys. **15**, 1515 (1982).
[23] M. R. Spender and A. H. Morrish, Solid State Commun. **11**, 1417 (1972).
[24] F. K. Lotgering, A. M. van Diepen, and J. F. Olijhoek, Solid State Commun. **17**, 1149 (1975).
[25] L. Brossard *et al.*, Phys. Rev. B **20**, 2933 (1979).
[26] M. S. Park *et al.*, Phys. Rev. B **59**, 10018 (1999).
[27] D. Maurer *et al.*, J. Appl. Phys. **93**, 9173 (2003).
[28] V. Tsurkan *et al.*, J. Appl. Phys. **90**, 4639 (2001).
[29] K. Matsuno *et al.*, Phys. Rev. Lett. **90**, 096404 (2003).
[30] A. P. Ramirez, G. P. Espinosa, and A. S. Cooper, Phys. Rev. Lett. **64**, 2070 (1990).
[31] G. Khaliullin and S. Maekawa, Phys. Rev. Lett. **85**, 3950 (2000).
[32] V. Tsurkan *et al.*, Phys. Rev. B **68**, 134434 (2003).